

General Information	1
Physical and Thermal Properties	3
Mechanical Properties	5
Hydrolytic Stability	6
Dimensional Stability	7
Thermal Aging	8
Electrical Properties	11
Effect of Humidity	12
Effect of Temperature	14
Effect of Frequency	16
Corona Life	18
Chemical Properties	19
Radiation Resistance	20
Kapton® Film Type Information	23
Nominal Construction, Type FN	23
Safety and Handling	25
Soldering and Hot Wire Stripping	25
Welding and Flame Cutting	25
Scrap Disposal	25
Fire Hazards	25
Static Electricity	25

Kapton® is used in applications such as the solar array and for thermal management in the United States space program.



General Information

Kapton® polyimide film possesses a unique combination of properties that make it ideal for a variety of applications in many different industries. The ability of Kapton® to maintain its excellent physical, electrical, and mechanical properties over a wide temperature range has opened new design and application areas to plastic films.

Kapton® is synthesized by polymerizing an aromatic dianhydride and an aromatic diamine. It has excellent chemical resistance; there are no known organic solvents for the film.

Kapton® does not melt or burn as it has the highest UL-94 flammability rating: V-0. The outstanding properties of Kapton® permit it to be used at both high and low temperature extremes where other organic polymeric materials would not be functional.

Adhesives are available for bonding Kapton® to itself and to metals, various paper types, and other films.

Kapton® polyimide film can be used in a variety of electrical and electronic insulation applications: wire and cable tapes, formed coil insulation, substrates for flexible printed circuits, motor slot liners, magnet wire insulation, transformer and capacitor insulation, magnetic and pressure-sensitive tapes, and tubing. Many of these applications are based on the excellent balance of electrical, thermal, mechanical, physical, and chemical properties of Kapton® over a wide range of temperatures. It is this combination of useful properties at temperature extremes that makes Kapton® a unique industrial material.

Three types of Kapton® are described in this bulletin:

- Kapton® Type HN, all-polyimide film, has been used successfully in applications at temperatures as low as -269°C (-452°F) and as high as 400°C (752°F).

Type HN film can be laminated, metallized, punched, formed, or adhesive coated. It is available as $7.5\ \mu\text{m}$ (0.3 mil), $12.5\ \mu\text{m}$ (0.5 mil), $19\ \mu\text{m}$ (0.75 mil), $25\ \mu\text{m}$ (1 mil), $50\ \mu\text{m}$ (2 mil), $75\ \mu\text{m}$ (3 mil), and $125\ \mu\text{m}$ (5 mil) films.

- Kapton® Type VN, all-polyimide film with all of the properties of Type HN, plus superior dimensional stability. Type VN is available as $12.5\ \mu\text{m}$ (0.5 mil), $19\ \mu\text{m}$ (0.75 mil), $25\ \mu\text{m}$ (1 mil), $50\ \mu\text{m}$ (2 mil), $75\ \mu\text{m}$ (3 mil), and $125\ \mu\text{m}$ (5 mil) films.
- Kapton® Type FN, a Type HN film coated on one or both sides with Teflon® FEP fluoropolymer resin, imparts heat sealability, provides a moisture barrier, and enhances chemical resistance. Type FN is available in a number of combinations of polyimide and Teflon® FEP thicknesses (see **Table 16**).

Note: In addition to these three types of Kapton®, films are available with the following attributes:


- antistat
- thermally conductive
- polyimides for fine line circuitry
- cryogenic insulation
- corona resistant
- pigmented for color
- conformable
- other films tailored to meet customers' needs

Data for these films are covered in separate product bulletins, which can be obtained from your DuPont representative.

The Chemical Abstracts Service Registry Number for Kapton® polyimide film is [25036-53-7].



Kapton® withstands the harsh chemical and physical demands on diaphragms used in automotive switches.

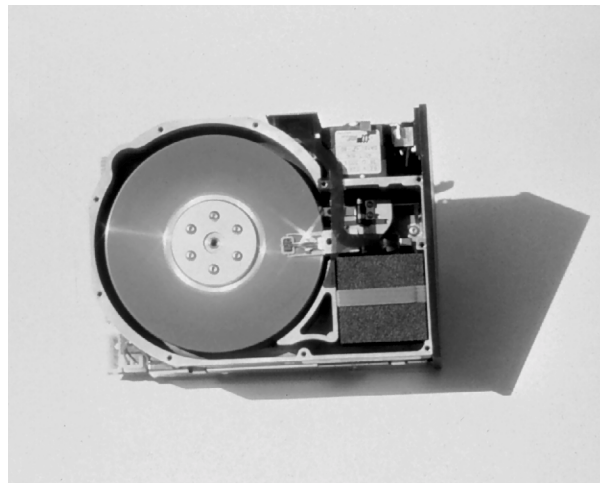

Kapton® is used in numerous electronic applications, including hard disk drives.

Physical and Thermal Properties

Kapton® polyimide films retain their physical properties over a wide temperature range. They have been used in field applications where the environmental temperatures were as low as -269°C (-452°F) and as high as 400°C (752°F).

Complete data are not available at these extreme conditions, and the majority of technical data presented in this section falls in the 23 to 200°C (73 to 392°F) range.

Table 1
Physical Properties of Kapton® Type 100 HN Film, 25 μm (1 mil)

Physical Property	Typical Value at		Test Method
	23°C (73°F)	200°C (392°F)	
Ultimate Tensile Strength, MPa (psi)	231 (33,500)	139 (20,000)	ASTM D-882-91, Method A*
Yield Point at 3%, MPa (psi)	69 (10,000)	41 (6000)	ASTM D-882-91
Stress to Produce 5% Elongation, MPa (psi)	90 (13,000)	61 (9000)	ASTM D-882-91
Ultimate Elongation, %	72	83	ASTM D-882-91
Tensile Modulus, GPa (psi)	2.5 (370,000)	2.0 (290,000)	ASTM D-882-91
Impact Strength, N-cm (ft-lb)	78 (0.58)		DuPont Pneumatic Impact Test
Folding Endurance (MIT), cycles	285,000		ASTM D-2176-89
Tear Strength—Propagating (Elmendorf), N (lbf)	0.07 (0.02)		ASTM D-1922-89
Tear Strength—Initial (Graves), N (lbf)	7.2 (1.6)		ASTM D-1004-90
Density, g/cc or g/mL	1.42		ASTM D-1505-90
Coefficient of Friction—Kinetic (Film-to-Film)	0.48		ASTM D-1894-90
Coefficient of Friction—Static (Film-to-Film)	0.63		ASTM D-1894-90
Refractive Index (Sodium D Line)	1.70		ASTM D-542-90
Poisson's Ratio	0.34		Avg. Three Samples Elongated at 5%, 7%, 10%
Low Temperature Flex Life	Pass		IPC TM 650, Method 2.6.18

*Specimen Size: 25 × 150 mm (1 × 6 in); Jaw Separation: 100 mm (4 in); Jaw Speed: 50 mm/min (2 in/min); Ultimate refers to the tensile strength and elongation measured at break.

Table 2
Thermal Properties of Kapton® Type 100 HN Film, 25 μm (1 mil)

Thermal Property	Typical Value	Test Condition	Test Method
Melting Point	None	None	ASTM E-794-85 (1989)
Thermal Coefficient of Linear Expansion	20 ppm/°C (11 ppm/°F)	-14 to 38°C (7 to 100°F)	ASTM D-696-91
Coefficient of Thermal Conductivity, W/m-K	0.12	296 K	ASTM F-433-77 (1987) ^{e1}
$\frac{\text{cal}}{\text{cm}\cdot\text{sec}\cdot^{\circ}\text{C}}$	2.87×10^{-4}	23°C	
Specific Heat, J/g-K (cal/g-°C)	1.09 (0.261)		Differential Calorimetry
Flammability	94V-0		UL-94 (2-8-85)
Shrinkage, %	0.17 1.25	30 min at 150°C 120 min at 400°C	IPC TM 650, Method 2.2.4A ASTM D-5214-91
Heat Sealability	Not Heat Sealable		
Limiting Oxygen Index, %	37		ASTM D-2863-87
Solder Float	Pass		IPC TM 650, Method 2.4.13A
Smoke Generation	DM = <1	NBS Smoke Chamber	NFPA-258
Glass Transition Temperature (T_g)	A second order transition occurs in Kapton® between 360°C (680°F) and 410°C (770°F) and is assumed to be the glass transition temperature. Different measurement techniques produce different results within the above temperature range.		

Table 3
Physical and Thermal Properties of Kapton® Type VN Film

Property	Typical Value for Film Thickness				Test Method
	25 μm (1 mil)	50 μm (2 mil)	75 μm (3 mil)	125 μm (5 mil)	
Ultimate Tensile Strength, MPa (psi)	231 (33,500)	234 (34,000)	231 (33,500)	231 (33,500)	ASTM D-882-91
Ultimate Elongation, %	72	82	82	82	ASTM D-882-91
Tear Strength—Propagating (Elmendorf), N	0.07	0.21	0.38	0.58	ASTM D-1922-89
Tear Strength—Initial (Graves), N	7.2	16.3	26.3	46.9	ASTM D-1004-90
Folding Endurance (MIT), $\times 10^3$ cycles	285	55	6	5	ASTM D-2176-89
Density, g/cc or g/mL	1.42	1.42	1.42	1.42	ASTM D-1505-90
Flammability	94V-0	94V-0	94V-0	94V-0	UL-94 (2-8-85)
Shrinkage, %, 30 min at 150°C (302°F)	0.03	0.03	0.03	0.03	IPC TM 650 Method 2.2.4A
Limiting Oxygen Index, %	37	43	46	45	ASTM D-2863-87

Table 4
Physical Properties of Kapton® Type FN Film*

Property	Typical Value for Film Type**		
	120FN616	150FN019	250FN029
Ultimate Tensile Strength, MPa (psi) 23°C (73°F) 200°C (392°F)	207 (30,000) 121 (17,500)	162 (23,500) 89 (13,000)	200 (29,000) 115 (17,000)
Yield Point at 3%, MPa (psi) 23°C (73°F) 200°C (392°F)	61 (9000) 42 (6000)	49 (7000) 43 (6000)	58 (8500) 36 (5000)
Stress at 5% Elongation, MPa (psi) 23°C (73°F) 200°C (392°F)	79 (11,500) 53 (8000)	65 (9,500) 41 (6000)	76 (11,000) 48 (7000)
Ultimate Elongation, % 23°C (73°F) 200°C (392°F)	75 80	70 75	85 110
Tensile Modulus, GPa (psi) 23°C (73°F) 200°C (392°F)	2.48 (360,000) 1.62 (235,000)	2.28 (330,000) 1.14 (165,000)	2.62 (380,000) 1.38 (200,000)
Impact Strength at 23°C (73°F), N·cm (ft·lb)	78 (0.58)	68.6 (0.51)	156.8 (1.16)
Tear Strength—Propagating (Elmendorf), N (lbf)	0.08 (0.02)	0.47 (0.11)	0.57 (0.13)
Tear Strength—Initial (Graves), N (lbf)	11.8 (2.6)	11.5 (2.6)	17.8 (4.0)
Polyimide, wt%	80	57	73
FEP, wt%	20	43	27
Density, g/cc or g/mL	1.53	1.67	1.57

* Test methods for **Table 4** are the same as for **Table 1**.

** Because a number of combinations of polyimide film and fluorocarbon coating add up to the same total gauge, it is necessary to distinguish among them. A three-digit system is used in which the middle digit represents the nominal thickness of the base Kapton® film in mils. The first and third digits represent the nominal thickness of the coating of Teflon® FEP fluoropolymer resin in mils. The symbol 9 is used to represent 13 μm (0.5 mil) and 6 to represent 2.5 μm (0.1 mil). Example: 120FN616 is a 120-gauge structure consisting of a 25 μm (1 mil) base film with a 2.5 μm (0.1 mil) coating of Teflon® on each side.

Mechanical Properties

The usual values of tensile strength, tensile modulus, and ultimate elongation at various temperatures can be obtained from the typical stress-strain curves shown in **Figures 1 and 2**. Such properties as tensile strength and modulus are inversely proportional to temperature,

whereas elongation reaches a maximum value at about 300°C (570°F). Other factors, such as humidity, film thickness, and tensile elongation rates, were found to have only a negligible effect on the shape of the 23°C (73°F) curve.

Figure 1. Tensile Stress-Strain Curves, Type HN Film, 25 μm (1 mil)


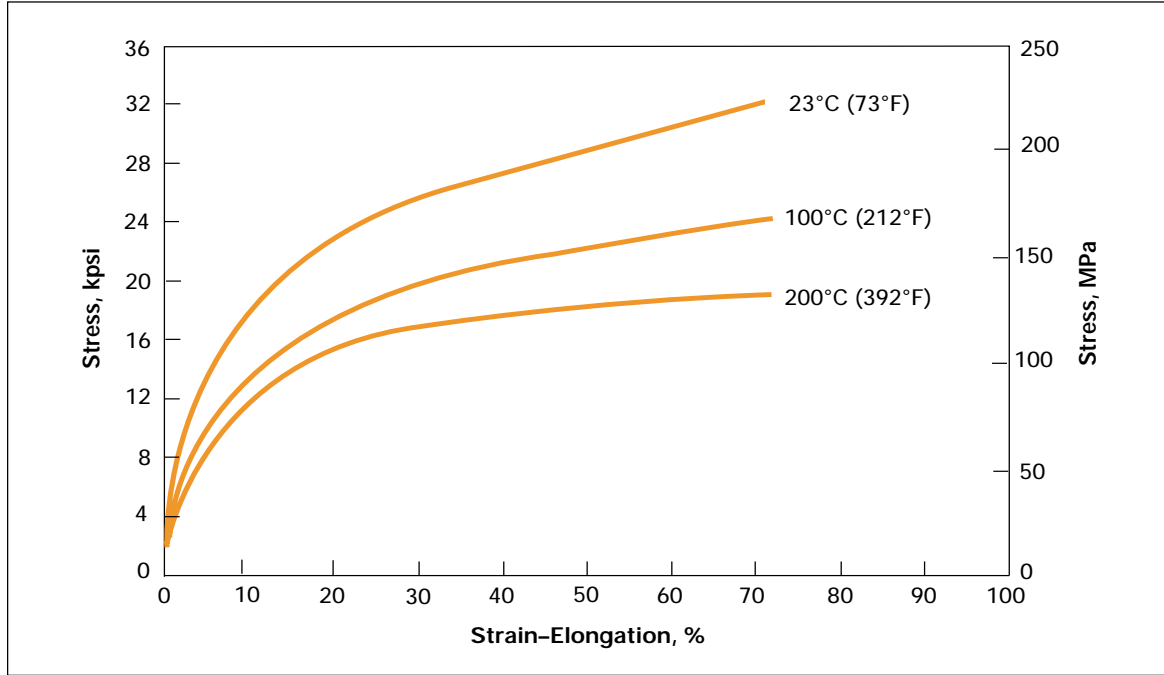


Figure 2. Tensile Creep Properties, Type HN Film, 25 μm (1 mil)

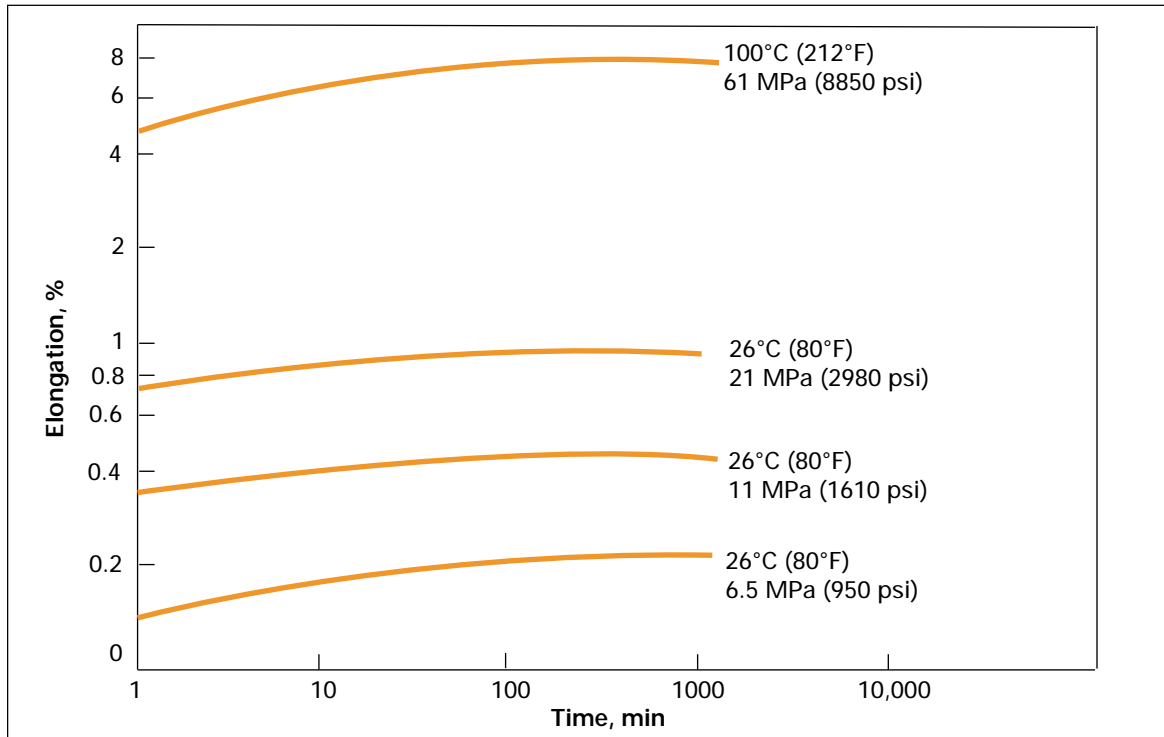

Hydrolytic Stability

Kapton® polyimide film is made by a condensation reaction; therefore, its properties are affected by water. Although long-term exposure to boiling water, as shown in the curves in **Figures 3** and **4**, will reduce the level of film properties, sufficient tensile and elongation

remain to ensure good mechanical performance. A decrease in the temperature and the water content will reduce the rate of Kapton® property reduction, whereas higher temperature and pressure will increase it.

Figure 3. Tensile Strength After Exposure to 100°C (212°F) Water, Type HN Film, 25 μm (1 mil)


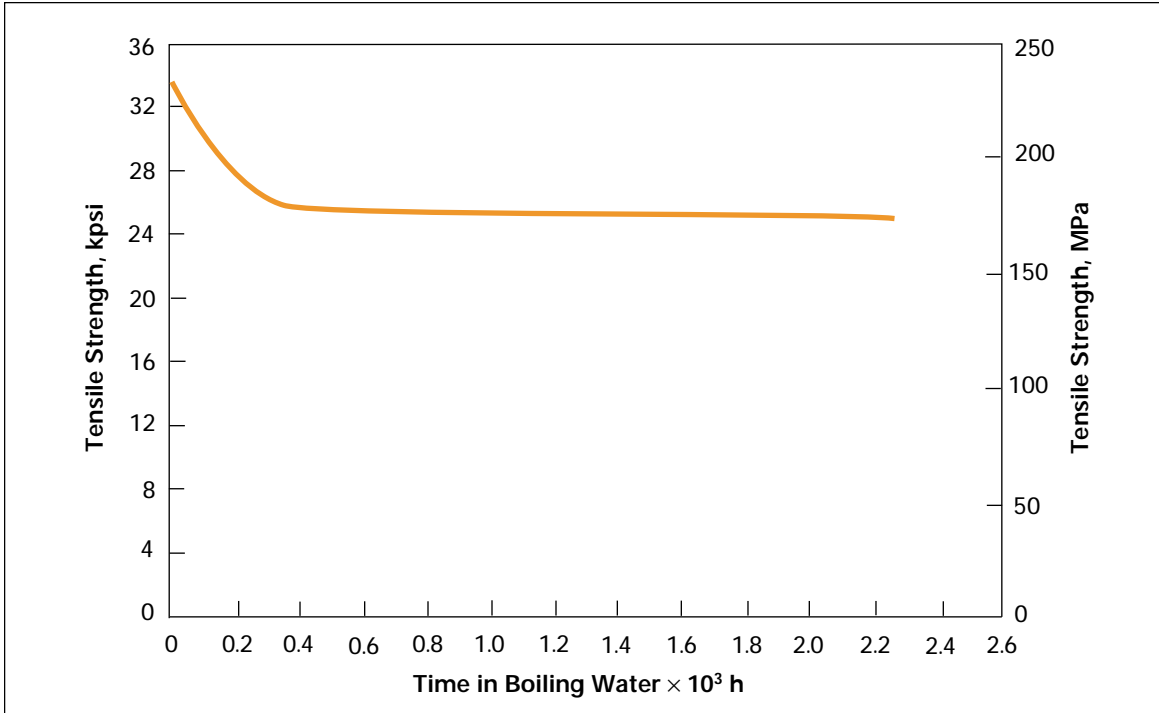


Figure 4. Ultimate Elongation After Exposure to 100°C (212°F) Water, Type HN Film, 25 μm (1 mil)

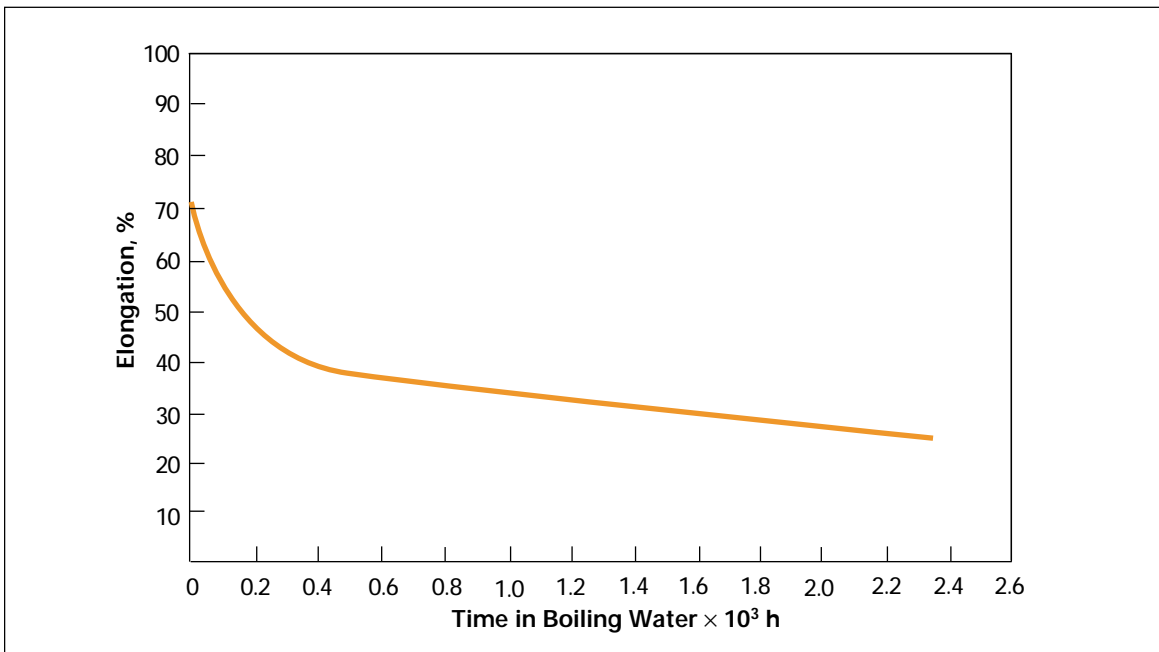


Dimensional Stability

The dimensional stability of Kapton® polyimide film depends on two factors—the normal coefficient of thermal expansion and the residual stresses placed in the film during manufacture. The latter causes Kapton® to

shrink on its first exposure to elevated temperatures as indicated in the bar graph in **Figure 5**. Once the film has been exposed, the normal values for the thermal coefficient of linear expansion as shown in **Table 5** can be expected.

Figure 5. Residual Shrinkage vs. Exposure Temperature and Thickness, Type HN and VN Films

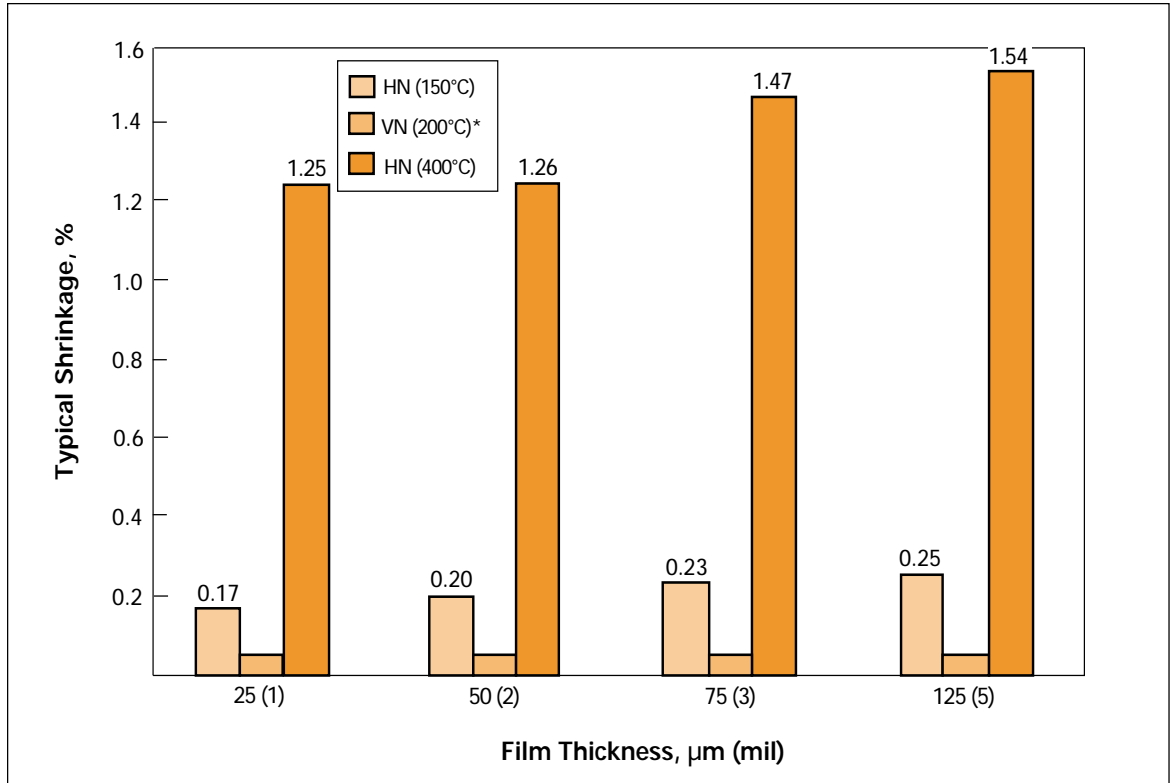

*Type VN shrinkage is 0.03% for all thicknesses.

**Table 5
Thermal Coefficient of Expansion,
Type HN Film, 25 µm (1 mil),
Thermally Exposed**

Temperature Range, °C (°F)	ppm/°C
30–100 (86–212)	17
100–200 (212–392)	32
200–300 (392–572)	40
300–400 (572–752)	44
30–400 (86–752)	34

Thermal Aging

The useful life of Kapton® polyimide film is a function of both temperature and oxygen concentration. In accordance with UL-746B test procedures, the thermal life of Kapton® was

determined at various temperatures. At time zero and 325°C (617°F), the tensile strength is 234 MPa (34,000 psi) and the elongation is 67%. The results are shown in **Figures 6–8**.

Figure 6. Tensile Strength vs. Aging in Air at 325°C (617°F), Type HN Film, 25 µm (1 mil)

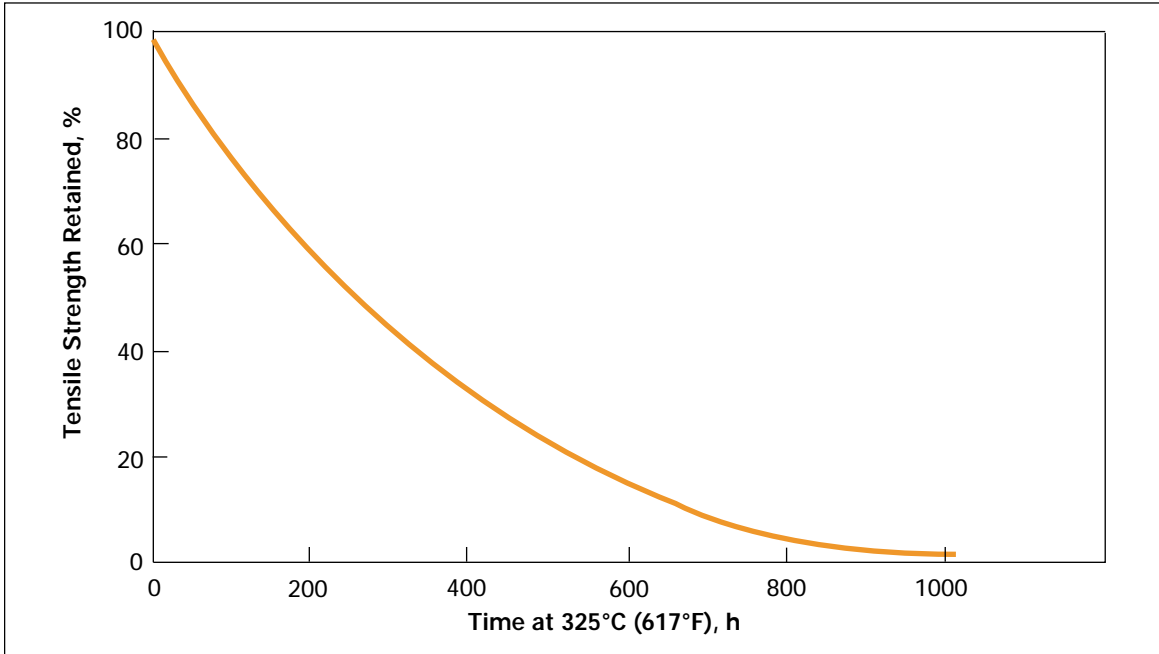


Figure 7. Ultimate Elongation vs. Aging in Air at 325°C (617°F), Type HN Film, 25 µm (1 mil)


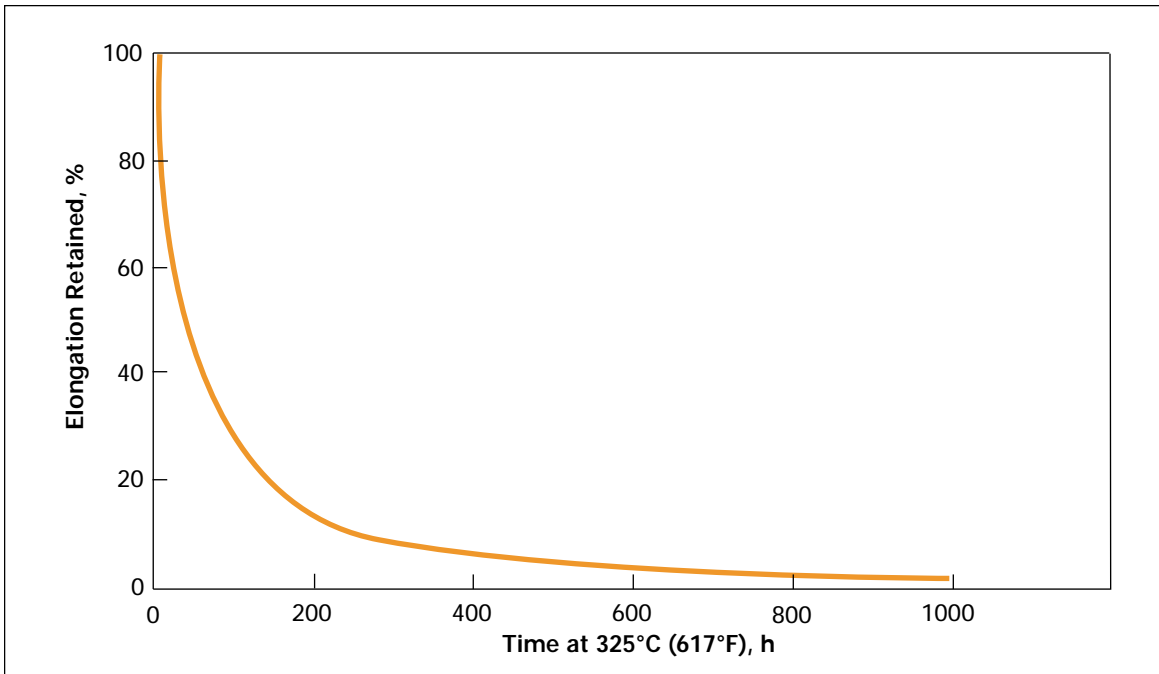



Figure 8. Retained Dielectric Strength at 325°C (617°F) for 25 μm (1 mil) Film, Test Method UL-746B

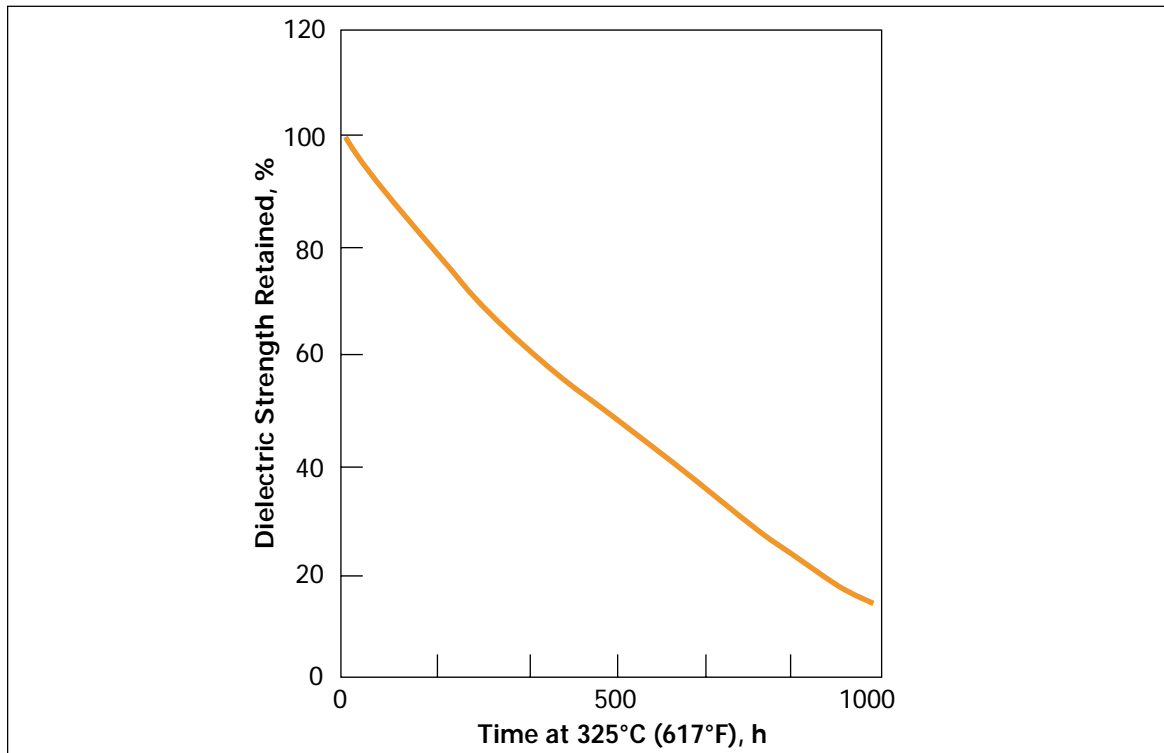

The life of Kapton® polyimide film at high temperature is significantly extended in a low-oxygen environment. Kapton® is subject to oxidative degradation. Hence, when it was tested in a helium environment, its useful life

was at least an order of magnitude greater than in air. Using a DuPont 1090 thermal analyzer system, the weight loss characteristics of Kapton® in air and helium at elevated temperatures are shown in **Figures 9 and 10**.

Figure 9. Weight Loss, Type HN Film, 25 μm (1 mil)*

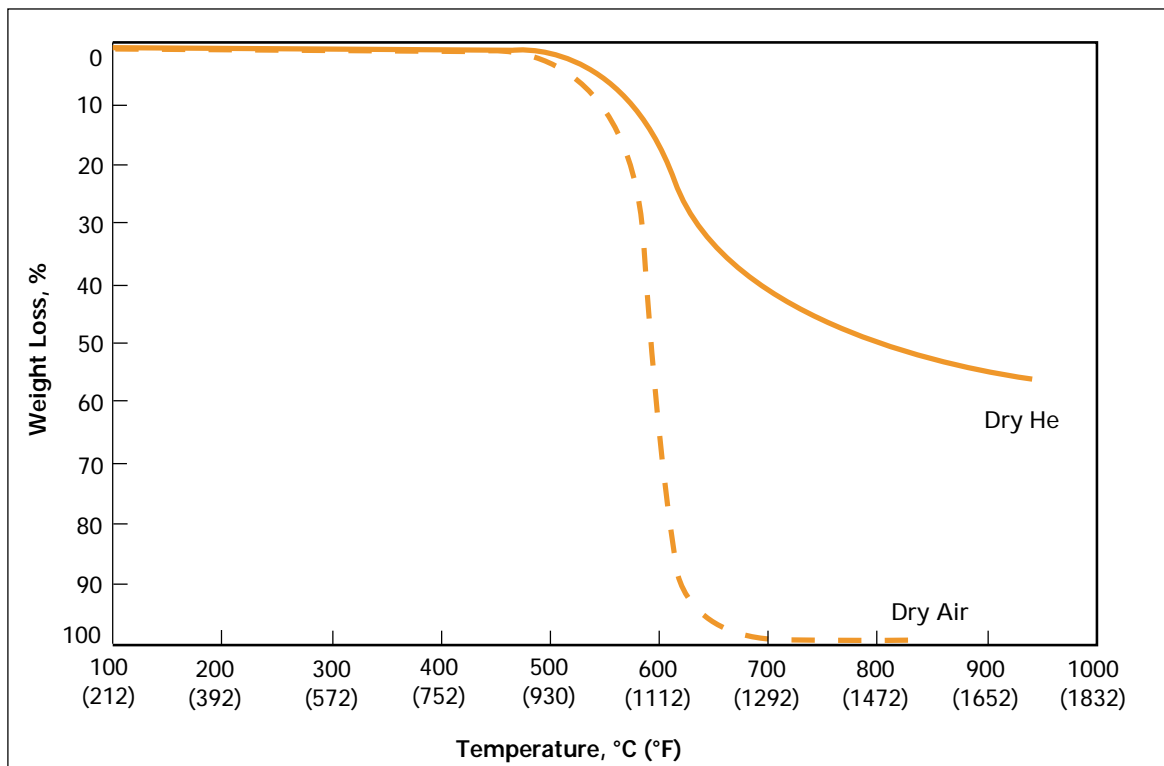


*Rate of temperature rise in °C (°F) was 3°C/min (5.4°F/min).

Table 6
Time Required for Reduction in Ultimate Elongation from 70% to 1%, Type HN Film, 25 μm (1 mil)

Temperature	Air Environment
450°C (840°F)	2 hours
425°C (800°F)	5 hours
400°C (750°F)	12 hours
375°C (710°F)	2 days
350°C (660°F)	6 days
325°C (620°F)	1 month
300°C (570°F)	3 months
275°C (530°F)	1 year
250°C (480°F)	8 years

Figure 10. Isothermal Weight Loss, Type HN Film, 25 μm (1 mil)

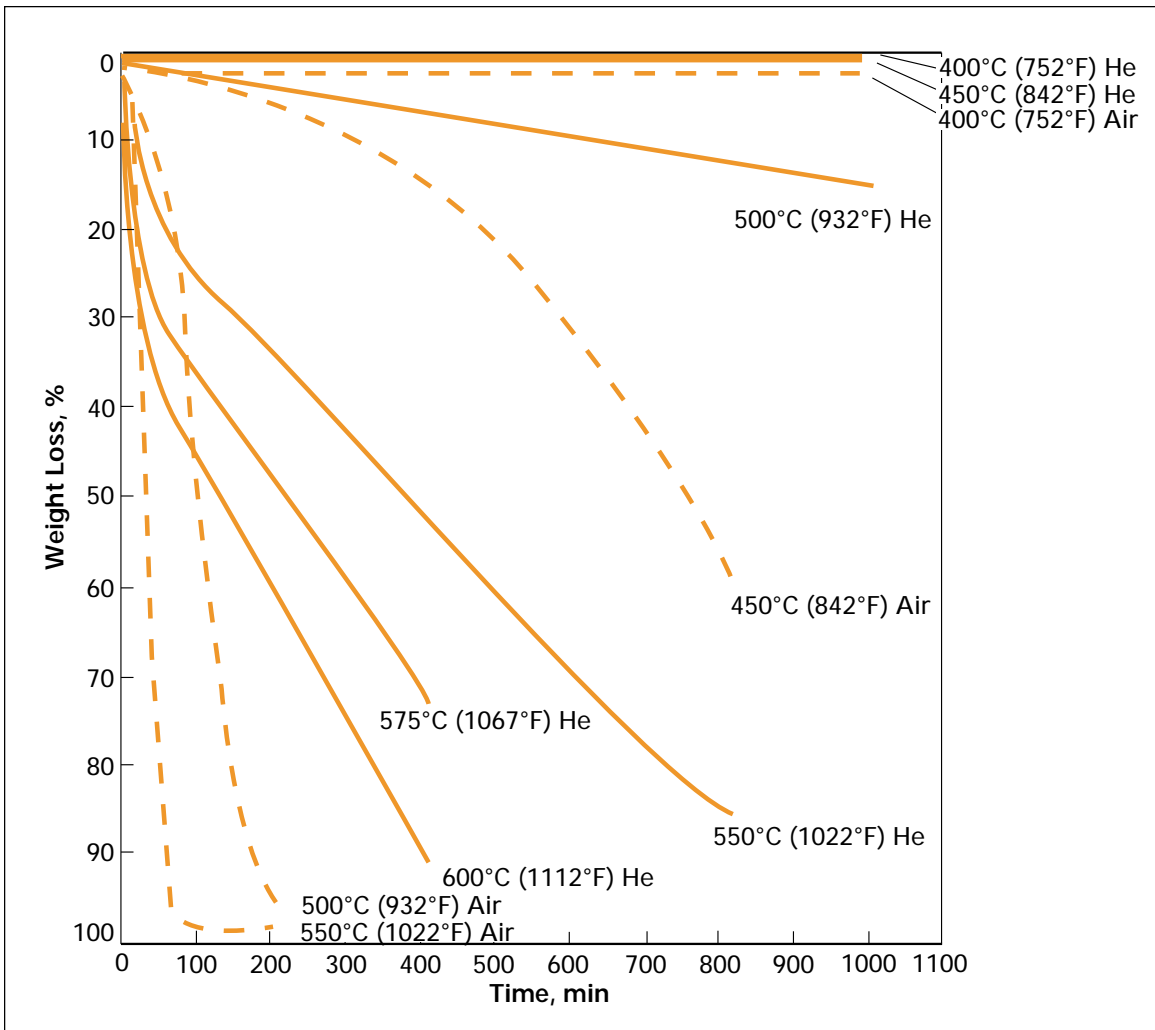

Electrical Properties

The most common electrical properties of Kapton® polyimide film of various gauges are shown in **Tables 6** and **7**. These values were measured at 23°C (73°F) and 50%

relative humidity. The effect of such factors as humidity, temperature, and frequency on these basic values can be found in **Table 9** and **Figures 11–13**.

Table 7
Typical Electrical Properties of Kapton® Type HN and VN Films

Property Film Gauge	Typical Value		Test Condition	Test Method
Dielectric Strength	V/μm (kV/mm)	(V/mil)	60 Hz	ASTM D-149-91 ^{e1}
25 μm (1 mil)	303	(7700)	1/4 in electrodes	
50 μm (2 mil)	240	(6100)	500 V/sec rise	
75 μm (3 mil)	205	(5200)		
125 μm (5 mil)	154	(3900)		
Dielectric Constant			1 kHz	ASTM D-150-92
25 μm (1 mil)		3.4		
50 μm (2 mil)		3.4		
75 μm (3 mil)		3.5		
125 μm (5 mil)		3.5		
Dissipation Factor			1 kHz	ASTM D-150-92
25 μm (1 mil)		0.0018		
50 μm (2 mil)		0.0020		
75 μm (3 mil)		0.0020		
125 μm (5 mil)		0.0026		
Volume Resistivity		Ω·cm		ASTM D-257-91
25 μm (1 mil)		1.5×10^{17}		
50 μm (2 mil)		1.5×10^{17}		
75 μm (3 mil)		1.4×10^{17}		
125 μm (5 mil)		1.0×10^{17}		

Table 8
Typical Electrical Properties of Kapton® Type FN Film

Property	120FN616	150FN019	250FN029
Dielectric Strength, V/μm (V/mil)	272 (6900)	197 (5000)	197 (5000)
Dielectric Constant	3.1	2.7	3.0
Dissipation Factor	0.0015	0.0013	0.0013
Volume Resistivity, Ω·cm			
at 23°C (73°F)	1.4×10^{17}	2.3×10^{17}	1.9×10^{17}
at 200°C (392°F)	4.4×10^{14}	3.6×10^{14}	3.7×10^{14}

Effect of Humidity

Because the water content of Kapton® polyimide film can affect its electrical properties, electrical measurements were made on 25 μm (1 mil) film after exposure to environments of

varying relative humidities at 23°C (73°F). The results of these measurements are shown in **Table 9** and **Figures 11–13**.

Table 9
Relative Humidity vs. Electrical Properties of Kapton®*
Type HN Film, 25 μm (1 mil)

Relative Humidity, %	Dielectric Strength, AC		Dielectric Constant	Dissipation Factor
	V/μm (kV/mm)	V/mil		
0	339	8600	3.0	0.0015
30	315	8000	3.3	0.0017
50	303	7700	3.5	0.0020
80	280	7100	3.7	0.0027
100	268	6800	3.8	0.0035

*For calculations involving absolute water content, 50% RH in our study is equal to 1.8% water in the film and 100% RH is equal to 2.8% water, the maximum adsorption possible regardless of the driving force.

Figure 11. AC Dielectric Strength vs. Relative Humidity, Type HN Film, 25 μm (1 mil)

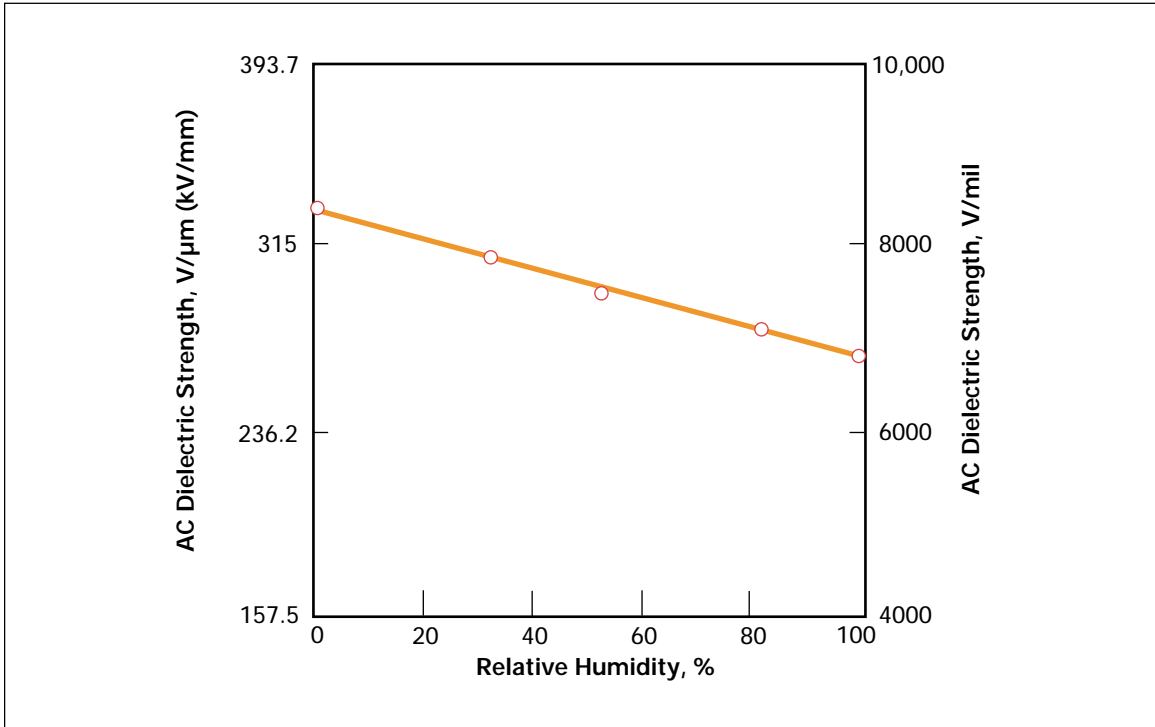


Figure 12. Dissipation Factor vs. Relative Humidity, Type HN Film, 25 μm (1 mil)


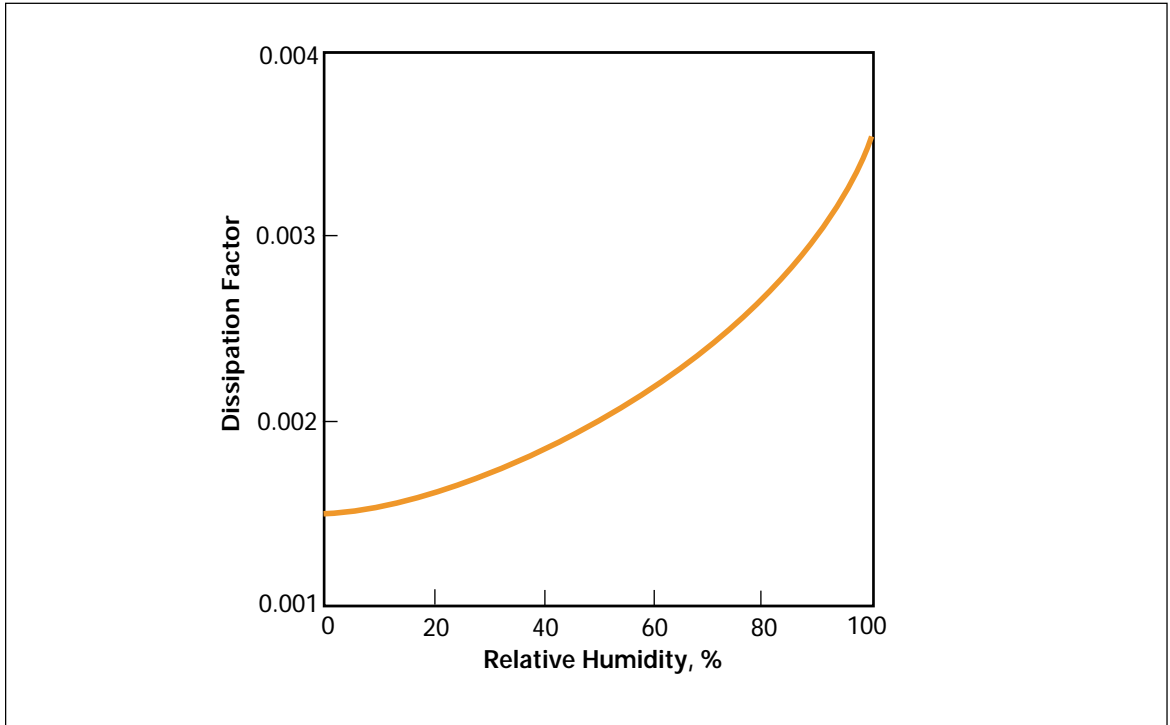


Figure 13. Dielectric Constant vs. Relative Humidity, Type HN Film, 25 μm (1 mil)

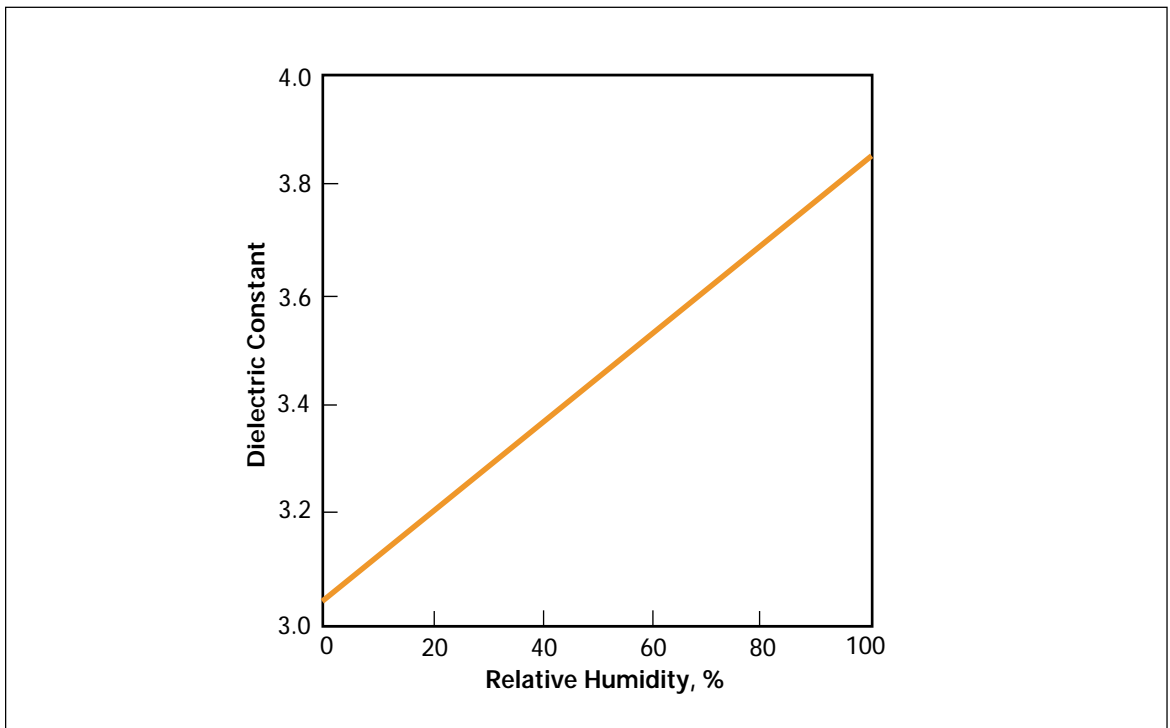

Effect of Temperature

As **Figures 14–17** indicate, extreme changes in temperature have relatively little effect on the excellent room temperature electrical properties of Kapton® polyimide film.

Figure 14. AC Dielectric Strength vs. Temperature, Type HN Film, 25 μm (1 mil)

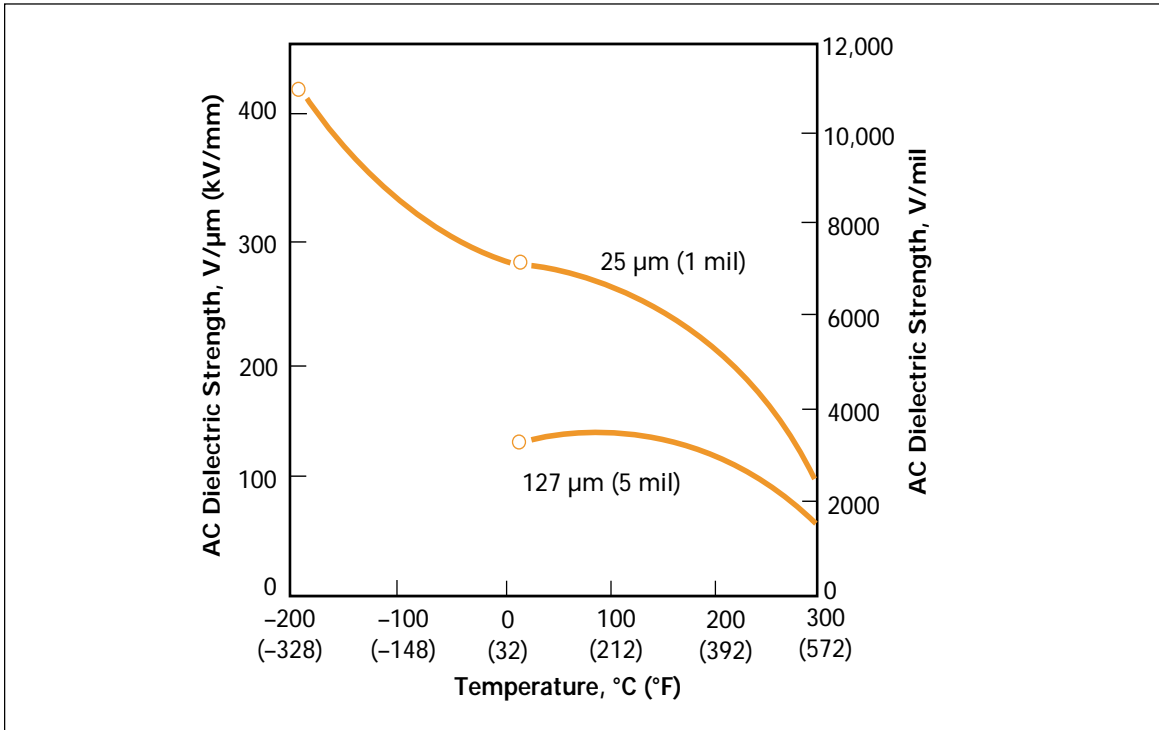


Figure 15. Dielectric Constant vs. Temperature, Type HN Film, 25 μm (1 mil)

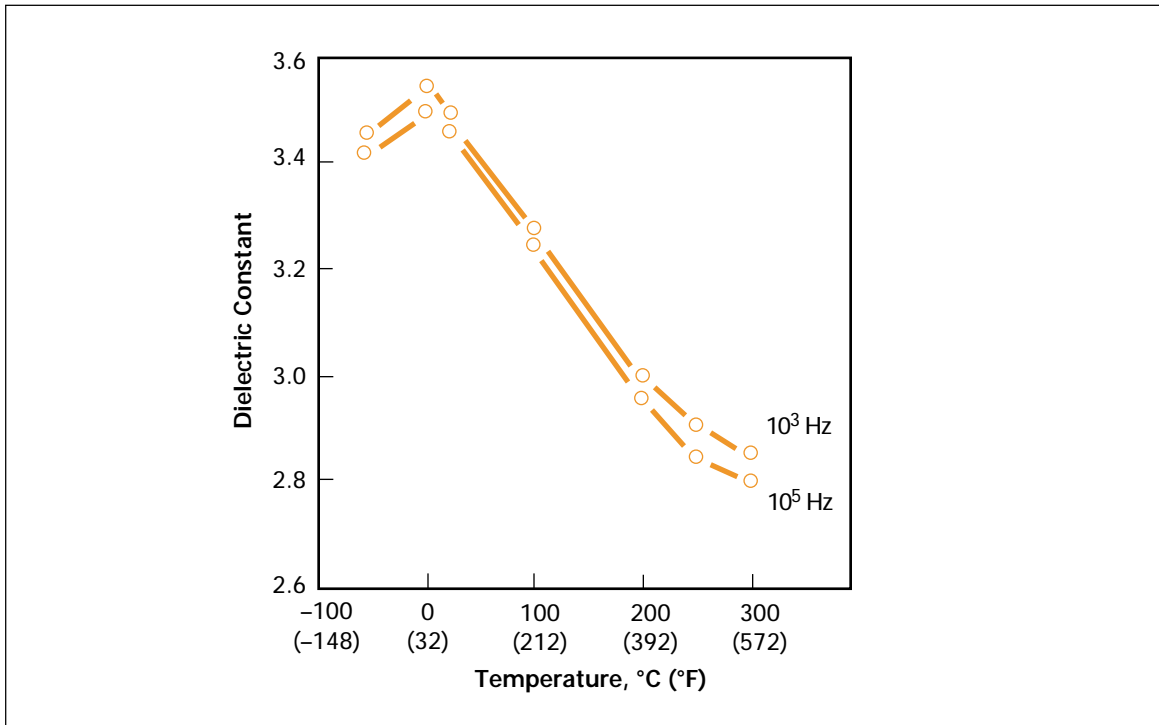


Figure 16. Dissipation Factor vs. Temperature, Type HN Film, 25 μm (1 mil)


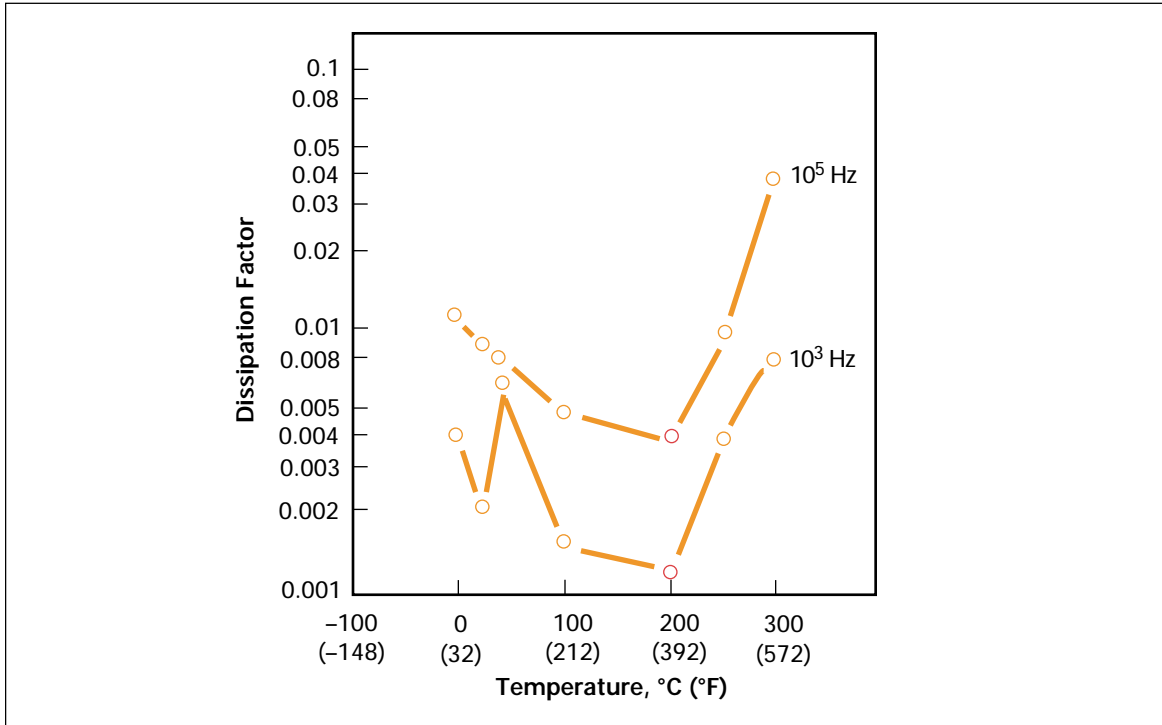


Figure 17. Volume Resistivity vs. Temperature, Type HN Film, 25 μm (1 mil)

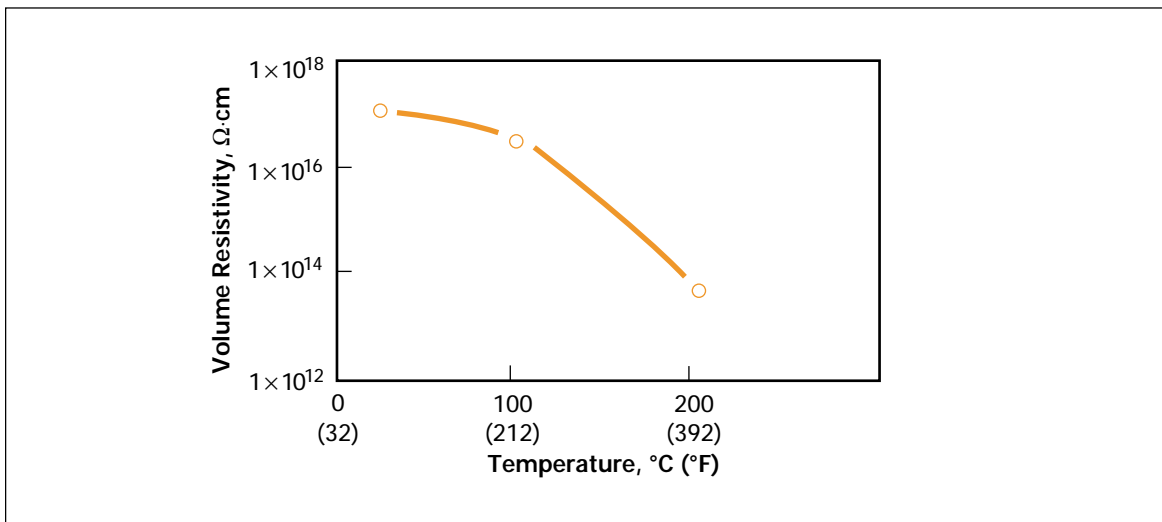

Effect of Frequency

The effect of frequency on the values of the dielectric constant and dissipation factor at various isotherms are shown in **Figures 18**

and **19** for Type HN film, 25 μm (1 mil), and in **Figures 20** and **21** for HN, 125 μm (5 mil).

Figure 18. Dielectric Constant vs. Frequency, Type HN Film, 25 μm (1 mil)

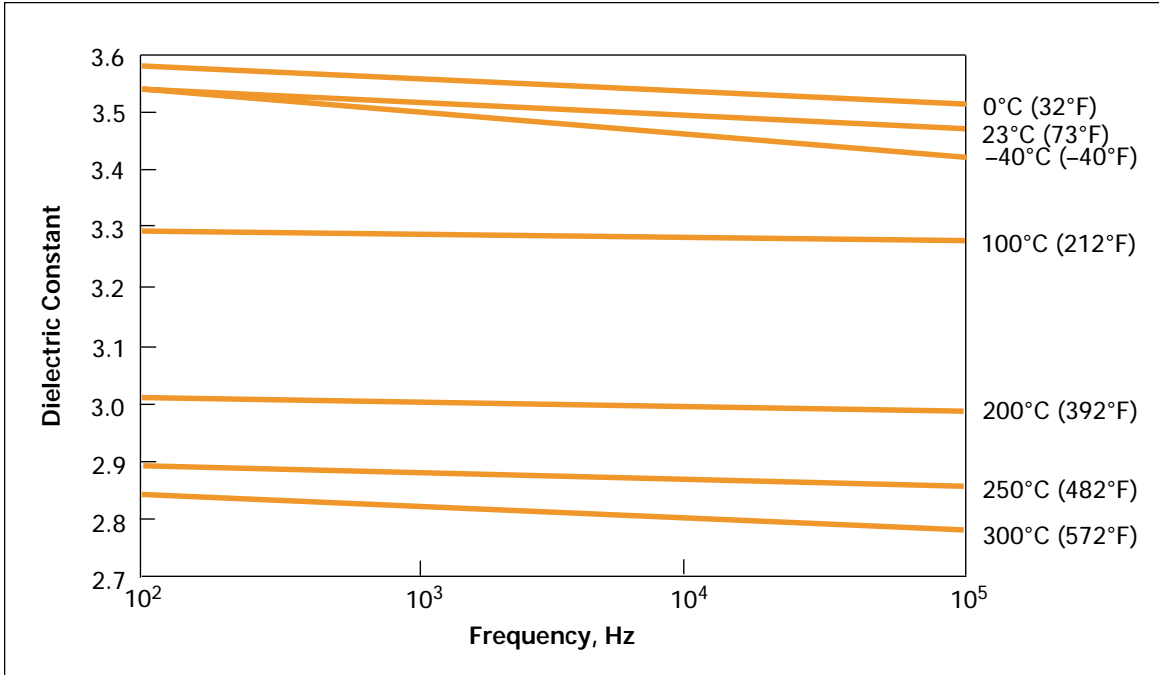


Figure 19. Dissipation Factor vs. Frequency, Type HN Film, 25 μm (1 mil)

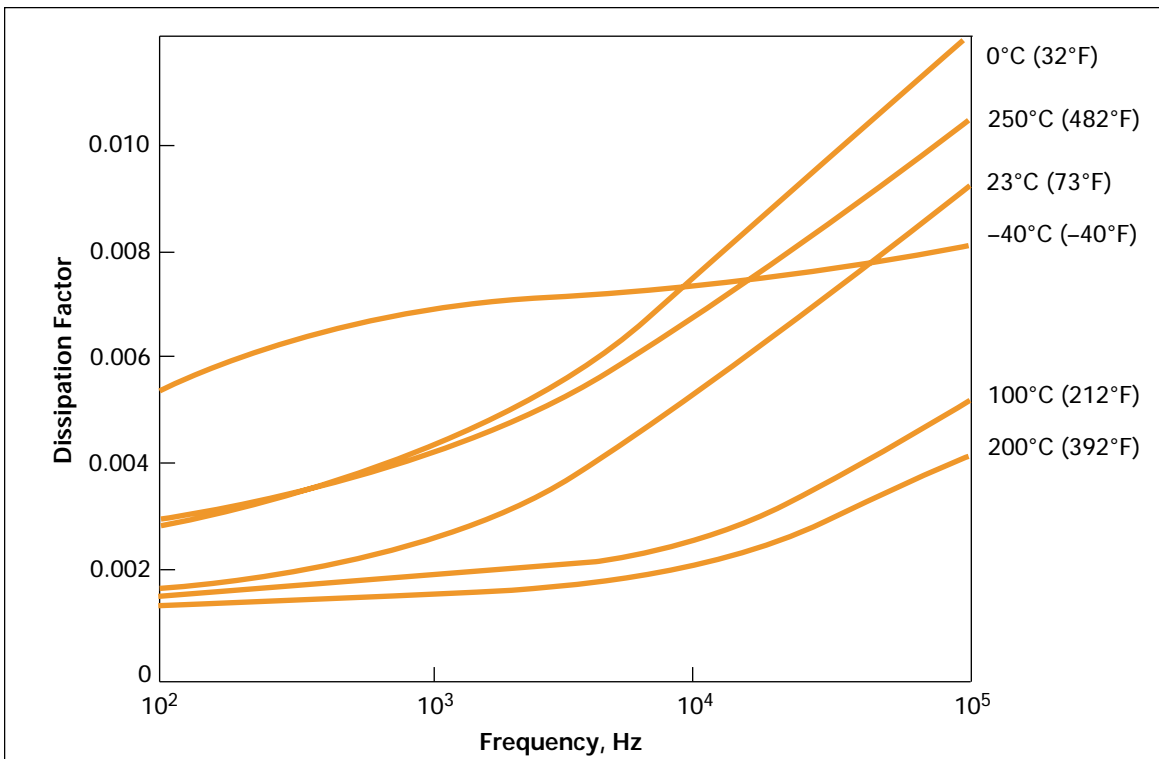


Figure 20. Dielectric Constant vs. Frequency, Type HN Film, 125 μm (5 mil)*


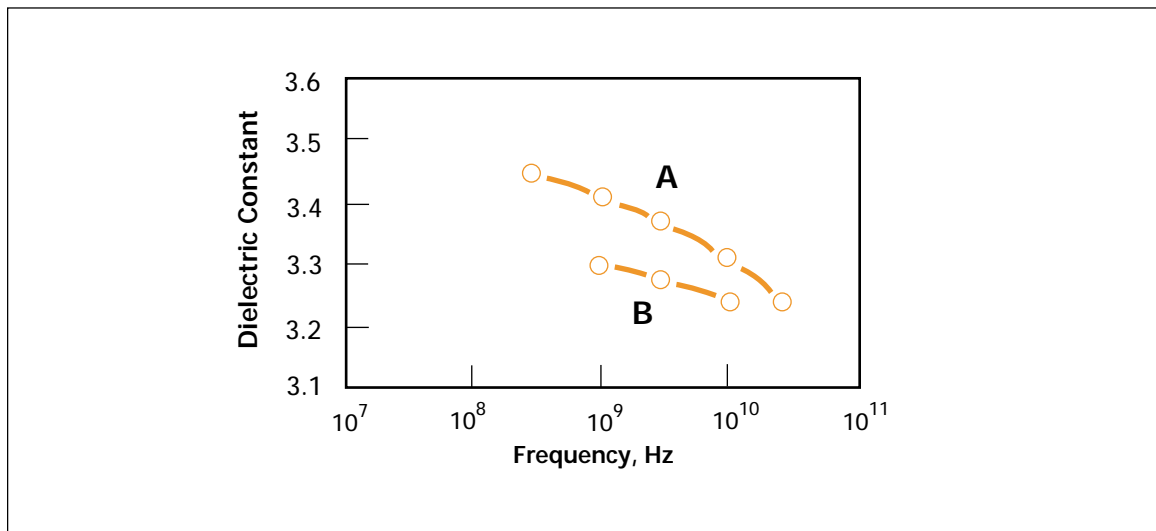


Figure 21. Dissipation Factor vs. Frequency, Type HN Film, 125 μm (5 mil)*

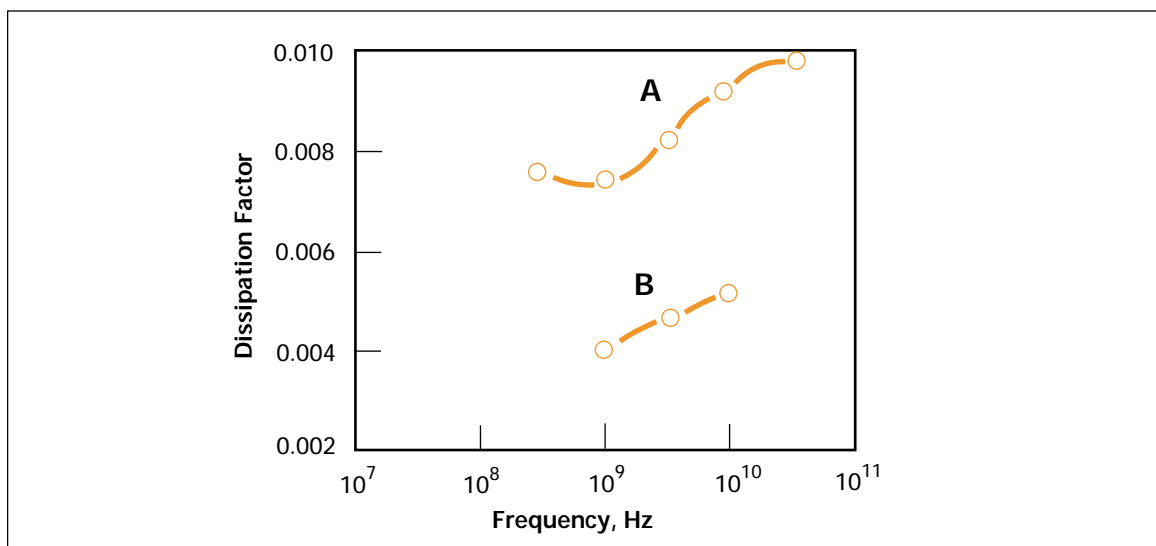

* Technical Report AFML-TR-72-39—Curve A is 500H Kapton® as received and measured at 25°C (77°F) and 45% RH with the electric field in the plane of the sheet. Curve B is the same measurement after conditioning the film at 100°C (212°F) for 48 h. Performance of 500HN is believed to be equivalent to 500H.

Corona Life


Like all organic materials, Kapton® is attacked by a corona discharge and when exposed continuously to it will ultimately fail dielectrically. At moderate levels of corona exposure, devices insulated with Kapton® have survived up to 3000 h, giving reasonable assurance that brief exposure to a corona will not significantly affect the life of a properly designed insulation system based on Kapton®.

Corona threshold voltage and intensity are functions of many parameters, including insulation thickness, air gap thickness, and device shape. Consult with a DuPont technical representative on the suitability of Kapton® for

specific applications where a corona may be present.

Figure 22 shows the life for 25 µm (1 mil) Kapton® HN polyimide film as a function of voltage (RMS) at 60 Hz. As the corona starting level is approached, the Kapton® life curve flattens, indicating a long life. It should be emphasized that the superior thermal and moisture-proof capabilities of Kapton® insulated magnet wire, wrappers, and slot insulation can be utilized without fear of corona in properly designed systems. Kapton® can be used alone or in combination with other insulation materials.

Figure 22. Voltage Endurance of 100HN Kapton® Polyimide Film*

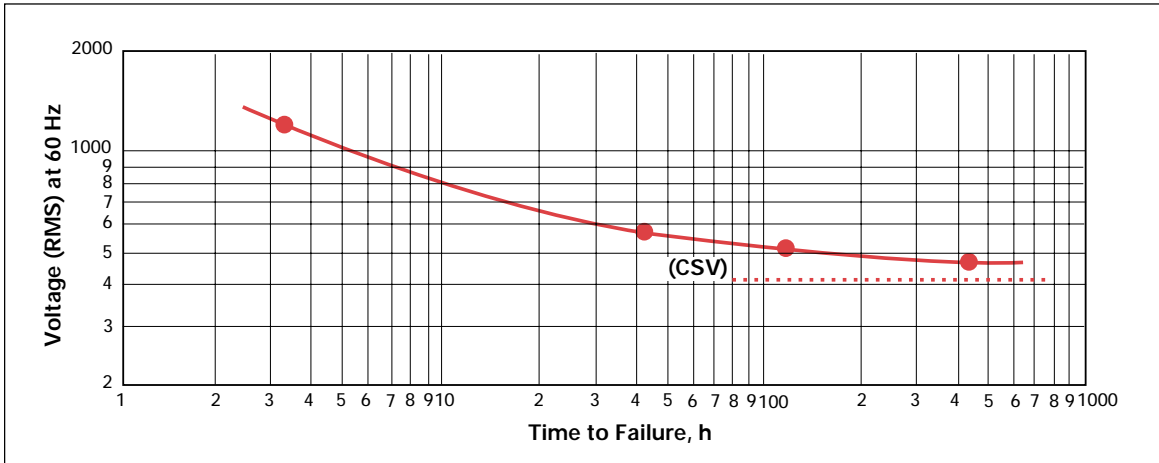

*Corona Starting Voltage (CSV) = 425 V

Chemical Properties

Typical chemical properties of Kapton® Types HN and FN films are given in **Tables 10** and **11**. The chemical properties of Type VN film are similar to those of Type HN.

Table 10
Chemical Properties of Kapton® Type HN Film, 25 µm (1 mil)

Property	Typical Value		Test Condition	Test Method
	Tensile Retained, %	Elongation Retained, %		
Chemical Resistance				
Isopropyl Alcohol	96	94	10 min at 23°C	IPC TM-650 Method 2.2.3B
Toluene	99	91		
Methyl Ethyl Ketone	99	90		
Methylene Chloride/ Trichloroethylene (1:1)	98	85		
2 N Hydrochloric Acid	98	89		
2 N Sodium Hydroxide	82	54		
Fungus Resistance				
	Nonnutrient			IPC TM-650 Method 2.6.1
Moisture Absorption				
	1.8% Types HN and VN		50% RH at 23°C	ASTM D-570-81 (1988) ^{e1} 24 h at 23°C (73°F)
	2.8% Types HN and VN		Immersion for	
Hygroscopic Coefficient of Expansion				
	22 ppm/% RH		23°C (73°F), 20–80% RH	
Permeability				
Gas	<i>mL/m²·24 h·MPa</i>	<i>cc/(100 in²·24 h·atm)</i>	23°C (73°F), 50% RH	ASTM D-1434-82 (1988) ^{e1}
Carbon Dioxide	6840	45		
Oxygen	3800	25		
Hydrogen	38,000	250		
Nitrogen	910	6		
Helium	63,080	415		
Vapor	<i>g/(m²·24 h)</i>	<i>g/(100 in²·24 h)</i>		ASTM E-96-92
Water	54	3.5		

Table 11
Chemical Properties of Kapton® Type FN Film

Property	120FN616	150FN019	400FN022
Moisture Absorption, % at 23°C (73°F), 50% RH	1.3	0.8	0.4
	2.5	1.7	1.2
Water Vapor Permeability, g/(m ² ·24 h)	17.5	9.6	2.4
	g/(100 in ² ·24 h)	1.13	0.62

Radiation Resistance

Because of its excellent radiation resistance, Kapton® is frequently used in high radiation environments where a flexible insulating material is required. In outer space, Kapton® is used both alone and in combination with other materials for applications that require radiation resistance at minimum weight. U.S. Government laboratory test data on gamma and neutron radiation exposure of Kapton® are summarized in **Tables 12** and **13**.

Testing the suitability of Kapton® for nuclear reactors and linear accelerators involves exposure to an adverse chemical environment in addition to radiation. For example, loss of coolant accident (LOCA) tests for qualification in containment areas in nuclear power plants expose the system to steam and sodium hydroxide, both of which tend to degrade Kapton®.

Accordingly, when Kapton® is used in nuclear power systems that require certification to IEEE-323 and -383, engineered designs that protect Kapton® from direct exposure to LOCA sprays are required.

The excellent ultraviolet resistance of Kapton® in the high vacuum of outer space is demonstrated by the data in **Table 14**. In the earth's atmosphere, however, there is a synergistic effect upon Kapton® if it is directly exposed to some combinations of ultraviolet radiation, oxygen, and water. **Figure 23** shows this effect as a loss of elongation when Kapton® was exposed in Florida test panels. **Figure 24** shows the loss of elongation as a function of exposure time in an Atlas Weatherometer. Design considerations should recognize this phenomenon.

Table 12
Effect of Gamma Radiation Exposure on Kapton® Polyimide Film
(Cobalt 60 Source, Oak Ridge)

Property	Control 1 mil Film	10 ⁴ Gy 1 h	10 ⁵ Gy 10 h	10 ⁶ Gy 4 d	10 ⁷ Gy 42 d
Tensile Strength, MPa psi × 10 ³	207 (30)	207 (30)	214 (31)	214 (31)	152 (22)
Elongation, %	80	78	78	79	42
Tensile Modulus, MPa (psi × 10 ³)	3172 (460)	3275 (475)	3378 (490)	3275 (475)	2903 (421)
Volume Resistivity Ω·cm × 10 ¹³ at 200°C (392°F)	4.8	6.6	5.2	1.7	1.6
Dielectric Constant 1 kHz at 23°C (73°F)	3.46	3.54	3.63	3.71	3.50
Dissipation Factor 1 kHz at 23°C (73°F)	0.0020	0.0023	0.0024	0.0037	0.0029
Dielectric Strength V/μm (kV/mm)	256	223	218	221	254

Table 13
Effect of Electron Exposure on Kapton® Polyimide Film Mixed
Neutron and Gamma

	5 × 10 ⁷ Gy	10 ⁸ Gy
5 × 10 ¹² neutrons/cm/s Flux at 175°C (347°F)	Film Darkened	Film Darkened and Tough

Table 14
Effect of Ultraviolet Exposure on Kapton® Polyimide Film*

	1000 h Exposure
Tensile Strength, % of Initial Value Retained	100
Elongation, % of Initial Value Retained	74

*Vacuum environment, 2×10^{-6} mmHg at 50°C (122°F). UV intensity equal to space sunlight to 2500A.

Figure 23. Effect of Florida Aging on Kapton® Polyimide Film




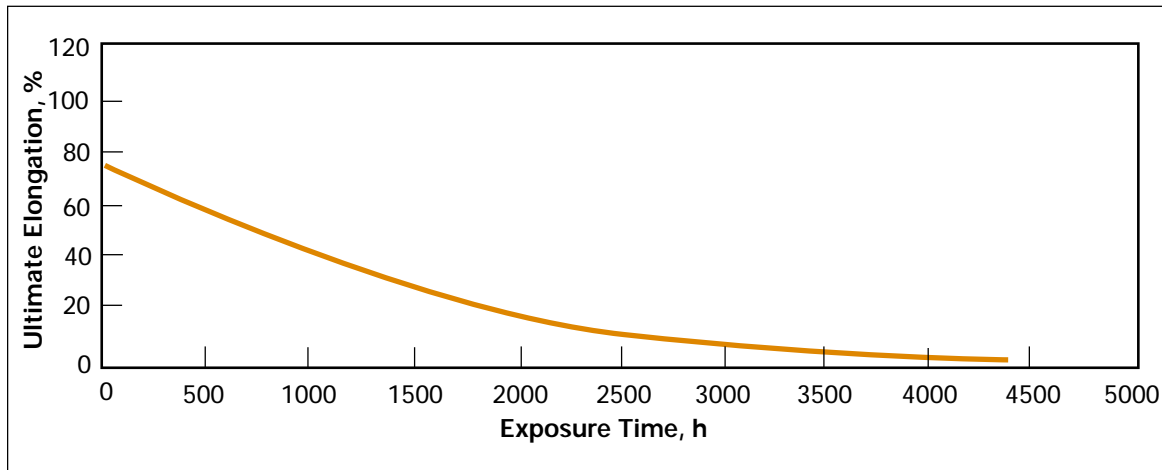


Figure 24. Effect of Weathering on Kapton® Polyimide Film (Atlas Weatherometer)

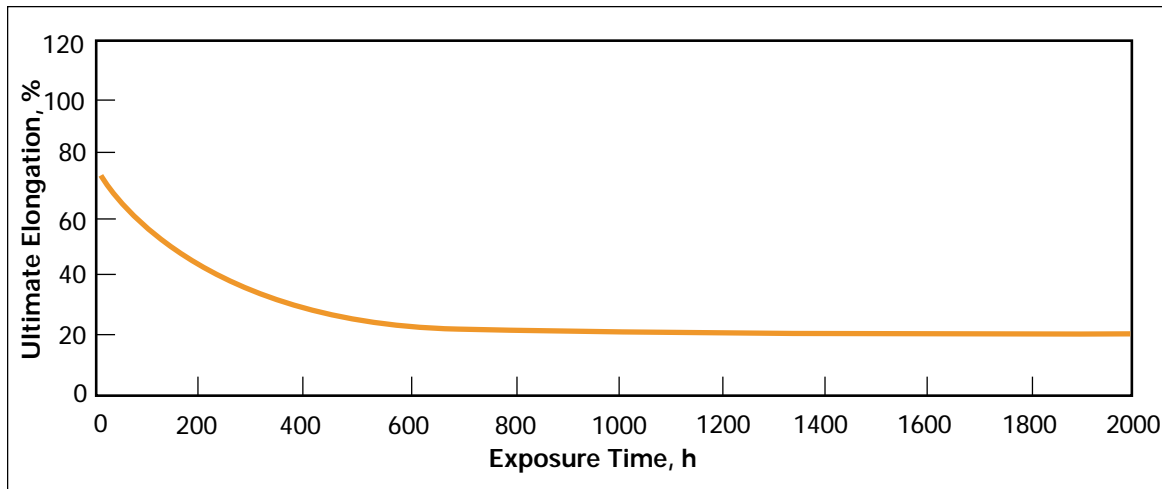

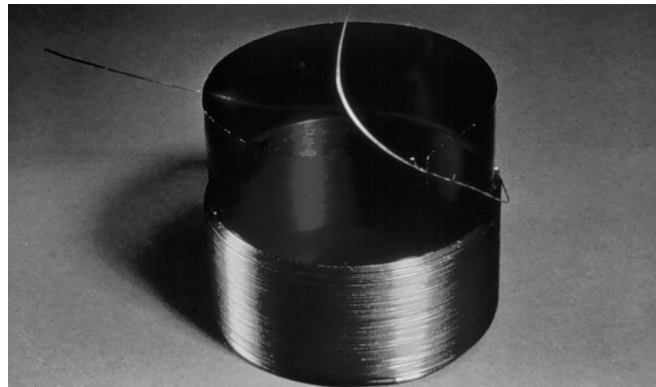

Kapton® is used as primary insulation for traction motors because of its outstanding combination of thermal, mechanical, and electrical properties.

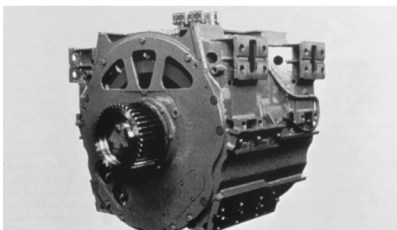

Voice coils made with Kapton® possess superior high-frequency sound performance at operating temperatures.

Kapton® Film Type Information

Table 15
Type and Thickness

Type	Nominal Thickness		Area Factor	
	µm	mil	m ² /kg	ft ² /lb
30HN	7.6	0.3	93	455
50HN	12.7	0.5	56	272
75HN	19.1	0.75	37	181
100HN	25.4	1.0	28	136
200HN	50.8	2.0	14	68
300HN	76.2	3.0	9.2	45
500HN	127	5.0	5.5	27
50VN	12.7	0.5	56	272
75VN	19.1	0.75	37	181
100VN	25.4	1.0	28	136
200VN	50.8	2.0	14	68
300VN	76.2	3.0	9.2	45
500VN	127	5.0	5.5	27
100FN099	25.4	1.0	23	110
120FN616	30.5	1.2	21	104
150FN999	38.1	1.5	14	68
150FN019	38.1	1.5	16	77
200FN011	50.8	2.0	11	54
200FN919	50.8	2.0	11	54
250FN029	63.5	2.5	10	49
300FN021	76.2	3.0	8.0	39
300FN929	76.2	3.0	8.0	39
400FN022	101.6	4.0	5.5	27
400FN031	101.6	4.0	6.1	30
500FN131	127	5.0	4.7	23
600FN051	152.4	6.0	4.3	21


Nominal Construction, Type FN

In the Kapton® Type FN order code of three digits, the middle digit represents the nominal thickness of the base Kapton® in mils. The first and third digits represent the nominal thickness of the coating of Teflon® FEP fluoropolymer resin in mils. The symbol 9 is used to represent 12.7 µm (0.5 mil) and 6 to represent 2.54 µm


(0.1 mil). Example: 120FN616 is a 120-gauge structure consisting of a 25.4 µm (1 mil) base film with a 2.54 µm (0.1 mil) coating of Teflon® on each side. Illustrated in **Table 16** are several examples of the many film types available.

Table 16
Type FN Film Constructions

Type	Construction					
	FEP		HN		FEP	
	µm	mil	µm	mil	µm	mil
100FN099			12.7	0.50	12.7	0.50
120FN616	2.54	0.10	25.4	1.00	2.54	0.10
150FN999	12.7	0.50	12.7	0.50	12.7	0.50
150FN019			25.4	1.00	12.7	0.50
200FN011			25.4	1.00	25.4	1.00
200FN919	12.7	0.50	25.4	1.00	12.7	0.50
250FN029			50.8	2.00	12.7	0.50
300FN021			50.8	2.00	25.4	1.00
300FN929	12.7	0.50	50.8	2.00	12.7	0.50
400FN022			50.8	2.00	50.8	2.00
400FN031			76.2	3.00	25.4	1.00
500FN131	25.4	1.00	76.2	3.00	25.4	1.00
600FN051			127	5.00	25.4	1.00

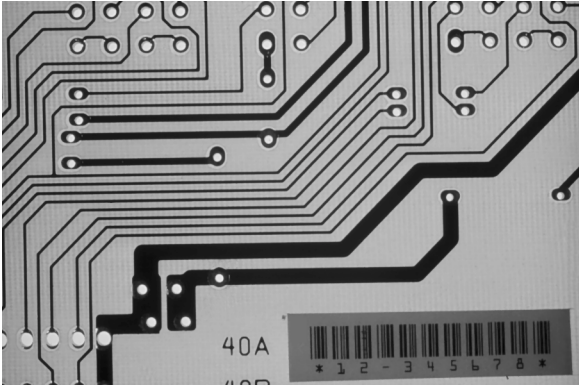

Kapton® bar code labels are used in the harsh environments PC boards are exposed to during soldering.

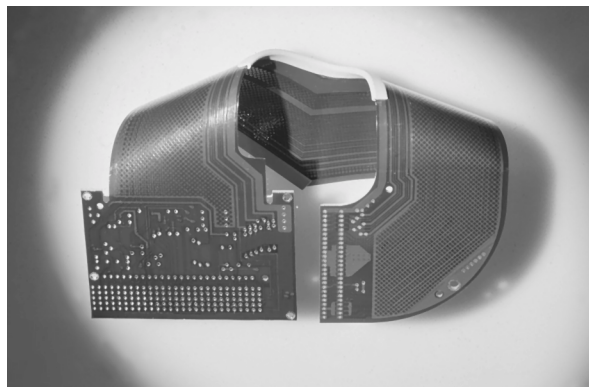

Kapton® is an excellent dielectric substrate that meets the stringent requirements of flexible circuitry.

Safety and Handling

Safe handling of Type HN and VN Kapton® polyimide films at high temperatures requires adequate ventilation. Meeting the requirements of OSHA (29 CFR 1910.1000) will provide adequate ventilation. If small quantities of Kapton® are involved, as is often the case, normal air circulation will be all that is needed in case of overheating. Whether or not existing ventilation is adequate will depend on the combined factors of film quantity, temperature, and exposure time. For additional information on the Teflon® FEP coating used on Type FN Kapton®, refer to the booklet “Guide to the Safe Handling of Fluoropolymer Resins” (H-48633).

Soldering and Hot Wire Stripping

Major uses for all types of Kapton® include electrical insulation for wire and cable and other electronic equipment. In virtually all of these applications, soldering is a routine fabricating procedure, as is the use of a heated element, to remove insulation. Soldering operations rarely produce off-gases to be of toxicological significance.

Welding and Flame Cutting

Direct application of welding arcs and torches can quickly destroy most plastics, including all types of Kapton® film. For practical reasons, therefore, it is best to remove all such parts from equipment to be welded. Where removal is not possible, such as in welding or cutting coated parts, mechanical ventilation should be provided. Because Kapton® can be used at very high temperatures, parts made from it may survive at locations close to the point of direct flame contact. Thus, some in-place welding operations can be done. Because the quantity of film heated is usually relatively small (less than 1 lb), ventilation requirements seldom exceed

those for normal welding work. Because of the possibility of inadvertent overheating, the use of a small fan or elephant-trunk exhaust is advisable.

Scrap Disposal

Disposal of scrap Kapton® polyimide films presents no special problem to the user. Small amounts of scrap may be incinerated along with general plant refuse. The incinerator should have sufficient draft to exhaust all combustion products to the stack. Care should be taken to avoid breathing smoke and fumes from any fire. Because Kapton® is so difficult to burn, it is often best to dispose of scrap film in a landfill.

Fire Hazards

Whether in storage or use, Kapton® is unlikely to add appreciably to the hazards of fire. Bulk quantities of Kapton® (over 100 lb) should be stored away from flammable materials.

In the event of fire, personnel entering the area should use a fresh air supply or a respirator. All types of chemical extinguishers may be used to fight fires involving Kapton®. Large quantities of water also may be used to cool and extinguish a fire.

Static Electricity

The processing of Kapton® can generate a strong static charge. Unless this charge is bled off as it forms by using ionizing radiation or tinsel, it can build to many thousand of volts and discharge to people or metal equipment. In dust- or solvent-laden air, a flash fire or explosion could result. Precautions for static charges should also be taken when removing plastic films used as protective packaging for Kapton®.

For additional information, users should refer to the bulletin “Kapton® Polyimide Film—Products of Decomposition” (H-16512).

United States

DuPont High Performance Films
P.O. Box 89
Route 23 South and DuPont Road
Circleville, OH 43113
Ordering Information:
(800) 967-5607
Product Information:
(800) 237-4357
Fax: (800) 879-4481

Canada

DuPont Canada, Inc.
P.O. Box 2200, Streetsville
Mississauga, Ontario, Canada
L5M 2H3
Inquiries: (905) 821-5603
Customer Service: (800) 263-2742
Fax: (905) 821-5230

Latin America

Argentina

DuPont Argentina
Av. Mitre y Calle 5
CP 1884, Berazategui, Argentina
Pcia de Buenos Aires
54-1-256-2435
Fax: 54-1-319-4451

Brazil

DuPont do Brasil
Al. Itapecuru, 506
06454-080, Alphaville
Barueri, Sao Paulo
55-11-421-8689
Fax: 55-11-421-8686

Mexico

DuPont S.A. de C.V.
Homero 206
Col. Chapultepec Morales
Mexico, D.F. 11570
525-722-1184
Fax: 525-722-1370

Venezuela

DuPont Venezuela
Edificio "Los Frailes"
Calle la Guarita
Urbanization Chuao
CP 1060, Caracas, Venezuela
58-2-92-8547
Fax: 58-2-91-5638

Europe

DuPont de Nemours
(Luxembourg) S.A.
Contern
L-2984 Luxembourg
Grand Duchy of Luxembourg
352-3666-5575
Fax: 352-3666-5000

Deutschland

DuPont de Nemours (Deutschland)
GmbH
DuPont Straße 1
D-61343 Bad Homburg v.d.H.
49-6172-87-2790
Fax: 49-6172-87-2930

France

DuPont de Nemours (France) S.A.
Z.A. de Courtaboeuf
3 Av. Du Canada—B.P. 85
F-91943 Les Ulis Cedex A
33-1-69 82 54 76
Fax: 33-1-69-82 54 98

Italy

DuPont de Nemours (Italy) S.p.A.
16, Via A. Volta
I-20093 Cologno Monzese (MI)
39-2-25-302 326
Fax: 39-2-25-43310

United Kingdom

DuPont (U.K.) Ltd.
Maylands Avenue
GB-Hemel Hempstead
Herts HP2 7DP
44-1442-21-8637
Fax: 44-1442-21-8639

Asia Pacific

Japan

DuPont Kabushiki Katsha
Arco Tower
8-1, Shimomeguro 1-chome
Meguro-ku, Tokyo 153
Japan
81-3-5434-6139
Fax: 81-3-5434-6193

ASEAN

DuPont Singapore Pte Ltd.
1 Maritime Square
#07-01 World Trade Centre
Singapore 099253
65-279-3434
Fax: 65-279-3456

Hong Kong/China

DuPont China Ltd.
1122 New World Office Bldg.
East Wing
Salisbury Road, Kowloon
Hong Kong
852-2734-5401
Fax: 852-2721-4117

India

DuPont South Asia Ltd.
503-505, Madhava
Bandra Kurla Commercial Complex
Bandra (E)
Bombay 400 051
India
91-22-6438255/6438256
Fax: 91-22-6438297

Korea

DuPont Korea Ltd.
4/5th Floor, Asia Tower
#726, Yeoksam-dong, Kangnam-ku
Seoul 135-082, Korea
82-2-222-5398
Fax: 82-2-222-5476

Taiwan

DuPont Taiwan Ltd.
7, Tsu-Chiang 1st Road
Chungli, Taoyuan
Taiwan, ROC
866-3-4549204
Fax: 866-3-4620676

Contact DuPont on the Internet at www.dupont.com.

The information given herein is based on data believed to be reliable, but DuPont makes no warranties express or implied as to its accuracy and assumes no liability arising out of its use by others. This publication is not to be taken as a license to operate under, or recommendation to infringe, any patent.

Caution: Do not use in medical applications involving permanent implantation in the human body. For other medical applications, see "DuPont Medical Caution Statement," H-50102.

